

# Comparative Evaluation of Microleakage of Bulk Fill Packable Resin Composite Restorations and Bulk Fill Flowable Resin Composite Restoration in Class V Cavity Preparation - An in Vitro Study

Dr. Gupta Amit Kumar,<sup>1</sup> Dr. Parvez Shahina,<sup>2</sup> Dr. Agarwal Manoj Kumar,<sup>3</sup>  
Dr. Likhyani Lalit<sup>4</sup>

**1. Dr. Gupta Amit Kumar**

Post Graduate Student, Department of Conservative Dentistry and Endodontics, RUHS College of Dental Sciences, Jaipur, Rajasthan

**2. Dr. Parvez Shahina**

Professor and HOD, Department of Conservative Dentistry and Endodontics, RUHS College of Dental Sciences, Jaipur, Rajasthan

**3. Dr. Agarwal Manoj Kumar**

Associate Professor, Department of Conservative Dentistry and Endodontics, RUHS College of Dental Sciences, Jaipur, Rajasthan

**4. Dr. Likhyani Lalit**

Associate Professor, Department of Conservative Dentistry and Endodontics, RUHS College of Dental Sciences, Jaipur, Rajasthan

## **Abstract**

**Aim and Objective:** Was to assess and compare the microleakage of bulk fill packable resin composite and bulk fill flowable resin composite in class V cavities along the occlusal and gingival margins using dye penetration test under stereomicroscope.

**Materials and Methods:** Hundred human extracted premolars were selected and randomly divided into 4 groups (n=25), as per the restorative materials for microleakage test. Group I: X-tra fil (Bulk fill packable resin composite). Group II: Power Fill (Bulk fill packable resin composite). Group III: SDR Flow Plus (Bulk fill flowable resin composite). Group IV Power Flow (Bulk fill flowable resin composite). Class V (box) cavities were prepared both on the buccal surfaces of each of the 100 teeth, a total of 100 cavities, restored, immersed in 2% methylene blue dye for 24 hours and then sectioned bucco lingually into two halves. Dye penetration score was measured along occlusal and gingival wall using a Stereomicroscope at 40X magnification. Statistical analysis was done using Chi square test for microleakage assessment. P value was set at <0.05.

**Result:** Intergroup comparison showed statistically no significant difference between the four groups both occlusal and gingival wall.

**Conclusion:** None of three resin composite materials were free from microleakage. All the four materials showed more microleakage at gingival wall compared to occlusal wall. Among all the tested groups Tetric power fill showed the least microleakage at the gingival wall.

**Keyword:** Microleakage, Class V, Resin composites.

## **INTRODUCTION**

Resin composite restorative materials were introduced in dentistry in 1950 and have developed tremendously over years. The use of composite restorations have become more popular in recent

decades because of their improved strength, esthetic quality, wear resistance, predictability and reduced water sorption as compared to earlier versions<sup>1</sup>. The major disadvantage of visible light cured composites is polymerization shrinkage. This shrinkage can

result in gap formation between the composite material and tooth structure, particularly if the restoration margin is placed in dentin or cementum. Bacteria, fluids, molecules, or ions can pass through this gap between the resin composite and the cavity wall, a process called microleakage. Microleakage is thought to be responsible for hypersensitivity, secondary caries, pulpal pathosis, and failure of restorations<sup>2</sup>.

Polymerization shrinkage of methacrylate based dental resin composites is unavoidable, due to the fact that monomer molecules are converted into a polymer network and therefore, exchanging van der Waals spaces in covalent bond spaces<sup>2</sup>. Contraction stress is the result of polymerization shrinkage taking place under confinement caused by bonding to cavity walls. The stress magnitude is affected by the volume of each increment and cavity configuration (C-factor), which are relatively larger in bulk-fill materials applications. Therefore, the stress control has been one of the main subjects in the material development<sup>3</sup>.

Various approaches have been employed in the formulation of bulk-fill composites to reduce the stress, adjust the stress generation kinetics and improve depth of cure. Those include changes in filler content and shape, modified monomer molecular weight and structure, addition of stress relievers and polymerization modulators, increase of polymerization inhibitors, new combinations of photoinitiators, enhanced material translucency and dual-cured polymerization mechanisms<sup>4</sup>.

Bulk-fill type of composite resins has been introduced in the market with a view to simplify the procedure of introducing the material into the cavity and its polymerization<sup>5</sup>. They may be used either as dentin replacement beneath conventional resin composite or as a single filling material. Bulk-fill composite can be light cured in a single increment up to 4 mm and it makes the work quicker by reducing the number of clinical steps<sup>6</sup>. Bulk-fill composite resins can be applied in thick layers due to low shrinkage of these materials and high filler content which causes shrinkage stresses to be very low<sup>6</sup>. Nevertheless, an ideal bulk-fill composite would be one that could be placed into a preparation having a high configuration factor (C-factor) design and still exhibited very little polymerization

shrinkage stress, while maintaining a high degree of cure throughout<sup>7</sup>.

In this study we compare the microleakage of two bulk fill packable resin composite restorations and two bulk fill flowable resin composite restoration in class v cavity preparation.

## **MATERIALS AND METHODOLOGY**

**Preparation of the specimens:** Class V (box) cavities were prepared on the buccal surfaces of 100 Premolar teeth, with a total of 100 cavities. The gingival cavosurface margin of the preparation was approximately 1.5 mm below the cemento-enamel junction and occlusal margin was approximately 1.5 mm above the cemento-enamel junction. The preparations were made with a No. 245 carbide bur (SS White) in a high speed standardized handpiece under copious water coolant. The dimension of the final cavity preparation was approximately 3.0 mm Occlusogingivally, 3.0 mm mesiodistally and 2 mm deep.

The preparations were etched with 37% phosphoric acid (Scotch bond Etchant, 3M ESPE) for 20 seconds, rinsed with water for 15 seconds and blot dried, leaving the dentin moist and shiny. An ethanol and water based adhesive system (ADPER single bond 2, 3M ESPE) was applied in two consecutive coats to the entire preparation, after 10 seconds of application gently air dried for 5 seconds and light cured for 20 seconds. Teeth were randomly divided into the four groups of 25 each corresponding to four different resin composites.

Group I: X-tra fil (Bulk fill packable resin composite), Group II: Tetric Power Fill (Bulk fill packable resin composite), Group III: SDR Plus (Bulk fill flowable resin composite) and Group IV: Tetric Power Flow (Bulk fill flowable resin composite). The specimens in each group were restored with the corresponding resin composite according to manufacturer's instructions. The restored specimens were stored in distilled water at 37°C for 12 hours. The restorations were then finished and polished with aluminium oxide disks (Sof-Lex Pop On, 3M ESPE). The teeth were coated with two layers of nail varnish leaving approximately 1.0 mm width around the restoration, to allow the contact of the tracing agent with the margin of the restoration. The specimens were thermocycled for 1000 cycles at 50°C and 55°C with

30 seconds of dwell time. The specimens were immediately immersed in 2% Methylene blue dye for 24 hours. The specimens sectioned through bucco lingual direction with a sectioning disc. Then the restorations were analyzed with a stereomicroscope at 40xmagnification and scored for degree of dye penetration along the occlusal and gingival walls.

### MICROLEAKAGE EVALUATION

Section of each tooth were evaluated at 40X with a stereomicroscope. The dye penetration for composite/tooth interface was scored for occlusal and gingival walls on a non-parametric scale from 0 to 4 based on the Ordinal ranking system, and the degree of leakage on the enamel and dentinal/cemental margins were determined.


0	No dye penetration
1	Dye penetration short of dentino-enamel junction (DEJ)/ cemento dentinal junction (CDJ).
2	Dye penetration up to dentino-enamel junction (DEJ)/ cemento-dentinal junction (CDJ)
3	Dye penetration beyond dentino-enamel junction( DEJ)/ cemento - dentinal junction (CDJ)
4	Dye penetration till/into the axial walls

**Table 1: The teeth were then divided into four groups of 25 each.**


Group	Composites	Composition
I	X-tra fil Voco America, Inc., Indian Land, USA. (Bulk fill packable resin composite)	<b>Monomers;</b> Bis-GMA, UDMA, TEGDMA, <b>Fillers;</b> 86% wt% (barium-boron-alumino-silicate glass)
II	Tetric Power Fill Ivoclar Vivadent AG, Schaan Liechtenstein. (Bulk fill packable resin composite)	<b>Monomers;</b> Bis-GMA, Bis-EMA, UDMA, Bis-PMA, DCP, D3MA. <b>Fillers;</b> Barium glass, Ytterbium, Trifluoride, Copolymer, Mixed Oxide (SiO <sub>2</sub> /ZrO <sub>2</sub> ) (79 wt%, 53–54 vol%)
III	SDR Plus Dentsply Sirona (York, USA) (Bulk fill flowable resin composite)	<b>Organic Matrix Composition:</b> Proprietary modified urethane dimetacrylate resin, TEGDMA; polymerizable dimethacrylate resin; polymerizable trimethacrylate resin; camphorquinone photoinitiator; ethyl-4(dimethylamino)benzoate photoaccelerator; butylated hydroxy toluene; fluorescent agent, and UV stabilizer. <b>Inorganic Filler Particulate:</b> (70.5 wt%, 47.4 vol%) barium-alumino-fluoro-borosilicate glass; silanated strontium alumino-fluoro-silicate glass; surface treated fume silicas; ytterbium fluoride; synthetic inorganic iron oxide pigments, and titanium dioxide
IV	Tetric Power Flow Ivoclar Vivadent AG, Schaan, Liechtenstein (Bulk fill flowable resin composite)	<b>Monomers;</b> Bis-GMA, Bis-EMA, UDMA, CMP-1E, DCP, D3MA. <b>Fillers;</b> Barium glass, Ytterbium, Trifluoride, Copolymer, Mixed Oxide (SiO <sub>2</sub> /ZrO <sub>2</sub> ) (71 wt%, 46–47 vol%)




**Figure 3: Extracted Premolar Teeth used for The Study**

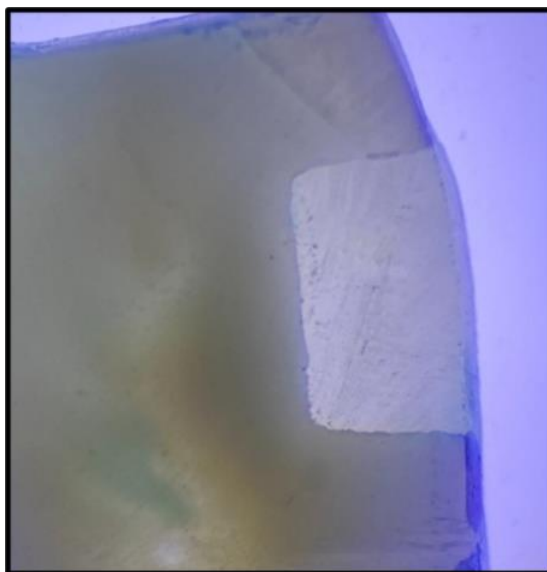


**The Arrow 1 & 2 Shows no dye Penetration at Tooth Composite Interface  
(Occlusal wall & Gingival wall Score 0)**

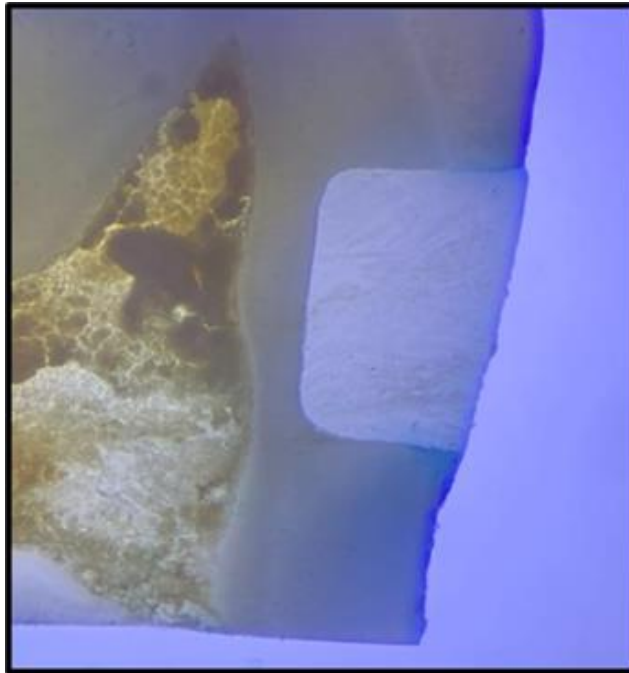


**The Arrow at interface 1 shows Dye penetration short of DEJ (Score 1)  
where as at interface 2 shows dye penetration beyond CDJ (Score 3)**

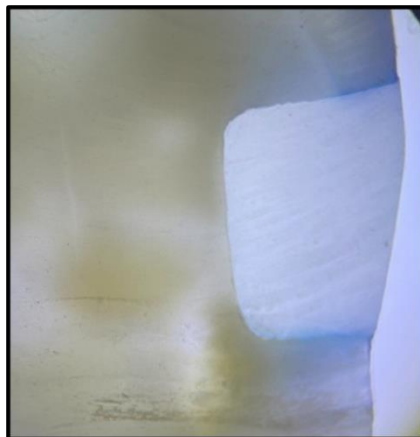

**The Arrow at interface 1 shows dye penetration up to DEJ (Score 2)  
where as at interface 2 shows dye penetration beyond CDJ (Score 3)**

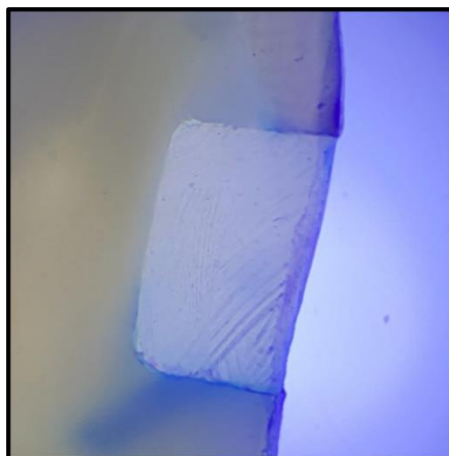

**The Arrow at interface 1 Shows Dye penetration beyond DEJ (Score 3)  
where as at interface 2 shows dye penetration till axial wall (Score 4)**

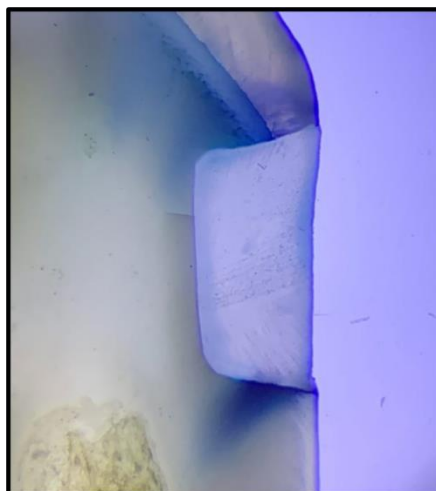

**The Arrow Shows Dye penetration till/into the axial walls**  
(Occlusal wall & Gingival wall Score 4)


### OBSERVATION AND RESULTS

The intergroup comparison of microleakage at occlusal and gingival wall of all the four study groups was done using Chi square test that showed a non significant difference between Groups I (X-tra fil), Group II (Tetric Power fill), Groups III (SDR Plus) and group IV (Tetric Power flow) ( $P > 0.05$ ), but least amount of microleakage was shown by group II (Tetric Power Fill), and maximum microleakage was seen in group IV (Tetric Power Flow).(Table 2 and 3). However there was a statistically significant difference seen for the

frequencies between groups when microleakage along occlusal wall and gingival wall was compared ( $p < 0.05$ ).(Table 4). Comparison of microleakage along occlusal wall and gingival wall between combined Packable vs Flowable composite resin, There was a statistically non significant difference seen for the frequencies between the groups ( $p > 0.05$ ). (Table 5 and Table 6). Thus, the results obtained from the present study showed that the least amount of microleakage was seen in Tetric Power Fill followed by X-tra Fil, SDR Plus , and the maximum was seen in Tetric Power Flow.

**Table 2: Shows intergroup comparison of microleakage along occlusal wall**


Groups	Occlusal wall dye penetration						Chi sq Value	p value of Chi sq test
	0	1	2	3	4	Total		
Group I X-tra fil	5	4	7	6	3	25(100)	9.711	0.469
Group II Tetric Power Fill	7	5	6	5	2	25(100)		
Group III SDR Plus	3	4	4	9	5	25(100)		
Group IV Tetric Power Flow	2	3	3	10	7	25(100)		

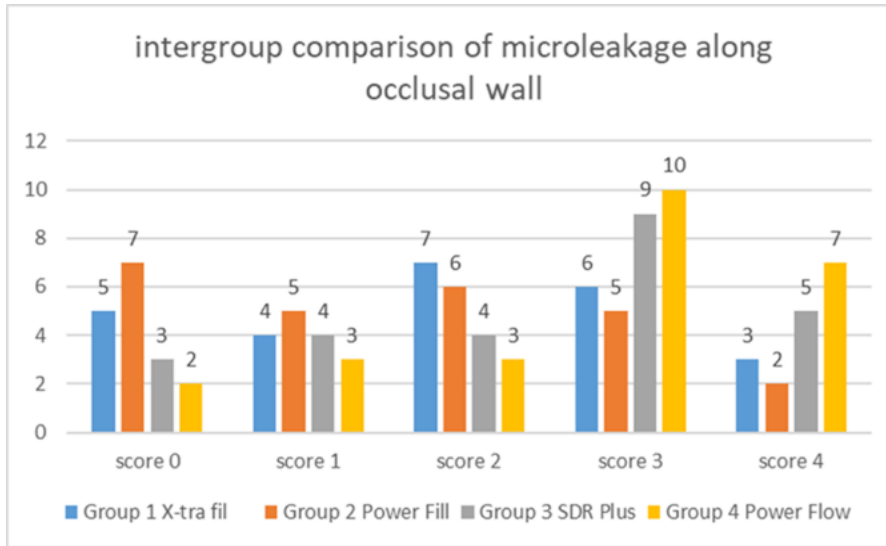

There was a statistically non significant difference seen for the frequencies between the groups ( $p>0.05$ )

**Table 3 : Shows intergroup comparison of microleakage along gingival wall**

Groups	Gingival wall dye penetration						Chi sq Value	p value of Chi sq test
	0	1	2	3	4	Total		
Group I X-tra fil	1	3	3	11	7	25(100)	13.039	0.366
Group II Tetric Power Fill	2	4	3	10	6	25(100)		
Group III SDR Plus	0	2	1	12	10	25(100)		
Group IV Tetric Power Flow	0	1	0	11	13	25(100)		

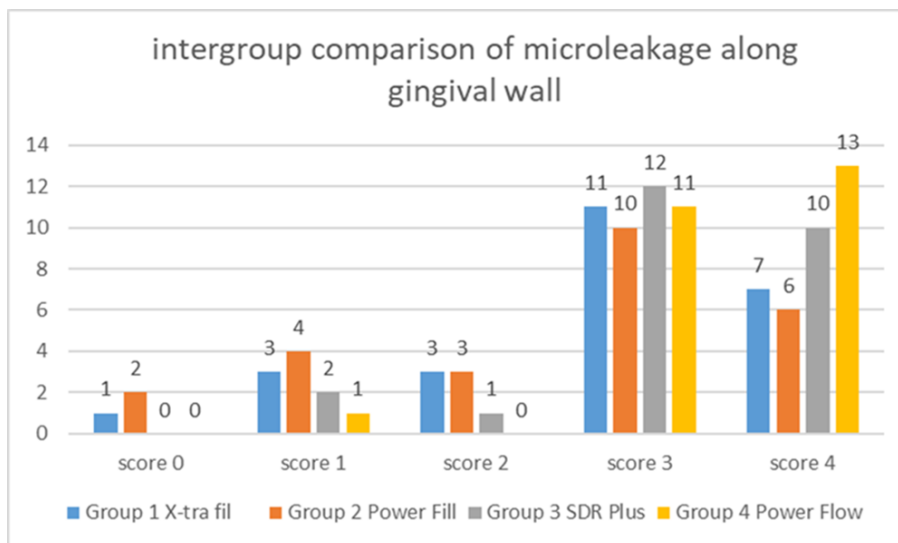

There was a statistically non significant difference seen for the frequencies between the groups ( $p>0.05$ )

## DISCUSSION

Resin composites are widely used for restoring cervical lesions. They are esthetic, mercury free and bond to tooth structure with the use of bonding systems<sup>59</sup>. The longevity of resin based composite depends on the interfacial bonding between resin and cavity walls, which should prevent the marginal microleakage that causes staining at the margins of restorations, recurrent caries, hyper sensitivity and pulp pathology<sup>66</sup>.

Microleakage is an important property that has been used in assessing the success of any restorative material used in restoring tooth. Improvements in resin composites have increased their usefulness as restorative materials; however, polymerization shrinkage continues to remain one of the primary deficiencies of composite restorations. Polymerization shrinkage causes contraction stress within the restoration that leads to microleakage, as well as stress within the surrounding tooth structure<sup>2</sup>.

The coefficient of linear thermal expansion of resin composites is three or four times that of tooth structure. In addition to the differences in thermal expansion coefficients, the shrinkage of composites during curing induces stresses at the tooth/restorative interface and generally results in gap formation. Therefore, polymerization shrinkage and the thermal expansion coefficient of these restorative materials have been suggested as major causes of microleakage<sup>67,68,69</sup>.

Other Possible reasons for microleakage at the tooth restoration margin are cavity configuration (C-factor), dentinal tubule orientation to the cervical wall (CEJ), organic content of dentine substrate and movement of dentinal tubular fluids, incomplete alteration or removal of smear layer by acidic primers (self-etch system) for adequate demineralization and hybrid layer formation, inefficient infiltration/ penetration of primer components into the demineralized collagen fibrils, physical characteristics of the restorative material, (filler loading, volumetric expansion, and modulus of elasticity), inadequate margin adaptation of restorative material, polymerization source photo initiator incompatibilities, and finishing and polishing effects<sup>2</sup>.

It is generally believed that the conventional composite materials should be polymerized in increments not thicker than 2mm. During the polymerization of a thicker increment, the material can pass through the gel point at different times at different depths. When the superficial material layers are already in post gel phase, the deeper layers have not yet reached the gel point. The superficial part of the material becomes firm, and the deeper part is still liquid. Application of large increments of material triggers a shrinkage stress rise, and therefore the reduction of this phenomenon is a particular challenge<sup>70,71</sup>.

The recommended alternative to layered techniques, the bulk-fill techniques, has taken up this challenge. The single increment application and polymerization method (the bulk-fill technique) proposed by the manufacturers of these composites did not compromise marginal adaptation of restorations. Bulk-fill composite materials evaluated in the present study seem to meet satisfactorily the requirements of this type of materials in terms of marginal adaptation. Bulk-fill composites are more translucent than other restorations, which allow the light to get to much deeper layers. The content of photo initiators of polymerization and stress inhibitors determines the optimal marginal seal of these composites<sup>72</sup>.

The current study examined the microleakage of different composite resins placed in class V cavities using a dye penetration test. In the present study, non carious Class V restorations were chosen for evaluation, because that the preparation of Class V cavities is minimal and their restoration is relatively easy, thereby reducing technique-sensitivity and operator-related variability. Secondly, Class V cavities have margins located both partly in enamel and partly in dentin. Moreover, class V cavities have high configuration factor (C-Factor). C-Factor is the ratio of bonded to the unbounded surface area. Class V restorations has high C-Factor (5) which is the reason for the internal bond disruption as well as microfissures around the restoration and cavity walls<sup>1,73</sup>.

To evaluate microleakage, methylene blue dye was used in this study. The diameter of dye molecules is 0.80nm that is less than the diameter of dentinal tubules (1-4 $\mu$ m) (Bayne and Thompson, 1998)<sup>51</sup>.



Thermocycling was done in this study because it is a widely used method in dental research, particularly when testing the performance of adhesive material. It aims at thermally stressing the adhesive joint at the tooth / restoration interface by subjecting the restored teeth to extreme temperatures encountered intraorally. This process may highlight the mismatch in thermal expansion between the restoration and tooth structure, resulting in different volumetric changes during temperature changes and causing fatigue of the adhesive joint with subsequent microleakage<sup>74</sup>. In this study Adper single bond II was used as a bonding agent for all the groups which may have influenced the marginal gap formation.

In this present study, There was a statistically non significant difference seen for the frequencies between the groups ( $p > 0.05$ ). But Tetric Power Fill (group II) showed least amount of microleakage scores followed by X-tra fil (Group I) , SDR Plus (group III) and the maximum was seen in Tetric Power flow (group IV). The possible reason that Tetric Power Fill showed lower microleakage was that Tetric Power Fill was optimized by including a ( $\beta$ -allyl sulfone) addition fragmentation chain transfer (AFCT) reagent. AFCT reagent pushes an uncontrolled radical chain growth polymerization reaction toward a step growth-like polymerization reaction<sup>4</sup>.

During standard polymerization, excited photo initiators create radicals which attack the double bonds of monomers resulting in methacrylate addition. It can lead to materials with an uncontrolled and inhomogeneous network architecture<sup>4</sup>.

In Tetric Power Fill, the radicals can potentially attack either a methacrylate double bond of a monomer resulting in methacrylate addition or the double bond of a  $\beta$ -allyl sulfone resulting in chain transfer. In the case of chain transfer, the growing radical chain is terminated by forming an intermediate radical that undergoes fragmentation and forms a sulfonyl radical and a new double bond. Essentially successive shorter chain formation is favoured over standard radical long-chain growth, leading to a delayed gel point and a more homogenous network<sup>4,10</sup>.

Gorsche et al. showed that the addition of an AFCT reagent to monomer formulations improved the

double-bond conversion and resulted in a more homogenous polymer network<sup>76</sup>. AFCT reagents therefore allow for a certain amount of control over the radical polymerization process. It is suggested that resultant materials should have reduced shrinkage stress, increased conversion and greater toughness<sup>77</sup>. Hee Young Park et al. showed allyl sulfide addition-fragmentation chain transfer reduces the final stress in ternary thiol-ene-methacrylate polymerizations by as much as 75% at high allyl sulfide concentrations<sup>75</sup>.

Other possible reason that Tetric Power Fill showed lower shrinkage than the conventional resin composite. This could be explained due to its pre-polymerized filler particles (shrinkage stress reliever) functionalized with silane, that seems to have relatively low elastic modulus (~10 GPa), causing it to act like a microscopic spring, attenuating the forces of shrinkage stress<sup>11,78</sup>.

Due to its low elastic modulus (10 GPa), the shrinkage stress reliever within Tetric PowerFill acts like a spring (expanding slightly as the forces between the fillers grow during polymerization) amongst the standard glass fillers which have a higher elastic modulus of 71 GPa. As a result, these Isofillers are capable of accommodating the tensile stresses that occur during polymerization<sup>11,78</sup>.

When comparing group II (Tetric Power Fill) and group IV (Tetric Power Flow) the result was statistically non significant ( $p > 0.05$ ). But Tetric Power Fill showed less microleakage than Tetric Power Flow. Due to the higher monomer and lower filler content, the amount of shrinkage in the flowable composites exceeds that of the sculptable composite<sup>10</sup>.

When comparing group III (SDR Plus) and group IV (Tetric power Flow), SDR Plus (group III) showed less microleakage than group IV. The possible reason could be: larger size of the SDR resin compared to conventional resin systems (molecular weight of 849 g/mol for SDR resin compared to 513 g/mol for Bis-GMA). The SDR technology comprises the unique combination of such a large molecular structure with a chemical moiety called a "Polymerization Modulator" chemically embedded in the center of the polymerizable resin backbone of the SDR resin monomer. The high molecular weight and the

conformational flexibility around the centered modulator impart optimized flexibility and network structure to SDR resin and it produce lower stress build up during polymerization<sup>9,79</sup>.

The microleakage scores of bulk fill SDR were in accordance with other similar studies conducted by Sahadev C K et al.<sup>80</sup> and MirosBaw OrBowski et al<sup>72</sup>.

When comparing group I and group II (packable resin composite) with group III and group IV (flowable resin composite), the result showed statistically non significant difference ( $p>0.05$ ). But packable resin composite (group I and group II) showed less microleakage than flowable resin composite (group III and group IV).

The possible reason could be: When the contents of the fillers increase, the contents of monomers decrease, resulting in a reduction of the total level of polymerization shrinkage and shrinkage stress and an increase in the flexural modulus of the material<sup>81</sup>.

Similar to our results, Jin-Young Kim et al. reported that high-viscosity conventional composites showed lower Volumetric Contraction than low-viscosity conventional composites<sup>8</sup>.

Similar to our results, Alagarsamy Venkatesh et al. reported that Filler volume fraction is inversely proportional to volumetric shrinkage. As the volume of filler content increases, the volume of resin matrix decreases and hence volumetric shrinkage reduces proportionately. The Monomer molecules which are held together by VanderWaals forces with the intermolecular distance of 0.3 nm - 0.4 nm are replaced by covalent bonds after their polymerization where the intermolecular distance is reduced to 0.15 nm. This reduction in the distance between the molecules leads to volumetric polymerization shrinkage<sup>82</sup>.

The present study also showed that microleakage at gingival margin in each of the groups was significantly more compared to the occlusal restoration. The possible reason could be: a) marginal seal at gingival margin restoration is less than occlusal which is due to better and stronger enamel band in occlusal because the enamel has an

inorganic and hemogenous structure, b) the absence of dentinal fluid in its structure has betterment infiltration of monomer in micro tags after etching and resulted in better micromechanical bond. But dentin is a dynamic substrate that contains a significant proportion of the water and organic matter that damages bonding system by the current adhesive process<sup>40</sup>. This was in accordance with previous studies done by Anil kumar S et al<sup>74</sup> and Kumar Gupta et al<sup>21</sup>.

De Munck et al<sup>83</sup> and Manhart et al<sup>84</sup> showed that the Microleakage in Class V restorations in the occlusal margin was significantly different with gingival margin and the microleakage at gingival margin was higher than the occlusal in all studies.

### **STUDY LIMITATIONS AND SCOPE FOR FURTHER STUDY**

The present study was done under in vitro conditions and used natural extracted teeth for restoration, and thermocycling was used as part of test protocol.

In vitro studies are very important for an early assessment of the dental material. However, only a clinical study takes into account, all the potential variables that vary from patient to patient. Some of the variables include masticatory forces, types of food, oral temperature, and humidity variations and presence of salivary enzymes and bacterial by-products.

Many new restorative materials are evolving rapidly, each with better properties and promising results for better performance. Therefore, further studies are required to establish the factual clinical worth of these materials to validate their in vitro established results.

### **CONCLUSION**

Within the limitations of the study,

1. None of four resin composite materials tested were free from microleakage.
2. All the four materials showed more microleakage at gingival wall compared to occlusal wall.
3. Tetric Power Fill showed the least microleakage at both occlusal and gingival walls.

## BIBLIOGRAPHY

1. Roberto R. Braga, Rafael Y. Ballester, Jack L. Ferracane. Factors involved in the development of polymerization shrinkage stress in resin-composites. *Dental Materials* (2005) 21, 962–970.
2. Sujatha Gopal Sooraparaju, Pavan Kumar Kanumuru, Surya Kumari Nujella, Karthik Roy Konda, K. Bala Kasi Reddy, and Sivaram Penigalapati. A comparative evaluation of microleakage in class V composite restorations. *International Journal of Dentistry* Volume 2014, page1-4.
3. David C. Watts, Julian D. Satterthwaite. Axial shrinkage-stress depends upon both C-factor and composite mass. *Dental Materials* 24 ( 2008 ) 1–8.
4. Juri Hayashi, Junji Tagami, Daniel Chan, Alireza Sadr. New bulk-fill composite system with high irradiance light polymerization. *Dental Material* xxx (2020).
5. Behery H, El-Mowafy O, El-Badrawy W, Nabih S, Saleh B. Gingival microleakage of class II bulk-fill composite resin restorations. *Dent Med Probl.* 2018;55(4):383–388.
6. Megha C Patel, Rohan K Bhatt, Disha A Makwani, Lipée D Dave, Vijeta S Raj. Comparative evaluation of marginal seal integrity of three bulk-fill composite materials in class II cavities. *Advances in Human Biology | Volume 8 | Issue 3 | September-December 2018.*
7. Alan Furness , Marko Yousef Tadros , Stephen W. Looney ,Frederick A. Rueggeberg. Effect of bulk/incremental fill on internal gap formation of bulk-fill composites. *Journal of Dentistry* 42(2014)439–449.
8. Burcu Oglakci , Derya Merve Halacoglu , Zümürüt Ceren Özduvan & Evrim Eliguzeloglu Dalkilic Volumetric change and gap formation in class V composite restorations. *Journal of Adhesion Science and Technology.* 2020
9. Scientific Manual SDR® Plus Bulk Fill Flowable (20.02.2018)  
[https://assets.dentsplysirona.com/flagship/en/exploration/restorative/sdr\\_flow\\_plus\\_eoc\\_version/SDR-Plus-Scientific-Manual.pdf](https://assets.dentsplysirona.com/flagship/en/exploration/restorative/sdr_flow_plus_eoc_version/SDR-Plus-Scientific-Manual.pdf).
10. Ivoclar Vivadent n.d. 3s PowerCure system. scientificdocument.  
<https://www.ivoclarvivadent.com/en/p/dental-professional/3s-powercure-product-system> [Accessed 3 February 2020].
11. Haidy N. Salem, Sherif M. Hefnawy, Shaymaa M. Nagi. Degree of conversion and polymerization shrinkage of low shrinkage bulk-fill resin composites. *Contemp Clin Dent* 2019;10:465-70.
12. Kaplan I, Mincer HH, Harris EF, Cloyd JS. Microleakage of composite resin and glass ionomer cement restorations in retentive and non retentive cervical cavity preparations. *The Journal of Prosthetic Dentistry.* 1992 Oct;68(4):616–23.
13. Hallett KB, Garcia-Godoy F. Microleakage of resin-modified glass ionomer cement restorations: An in vitro study. *Dental Materials.* 1993 Sep 1;9(5):306–11.
14. França FMG, Aguiar FHB, Santos AJS dos, Lovadino JR. Quantitative evaluation of microleakage in class V cavities using one-bottle and self-etching adhesive systems. *Braz oral res.* 2004 Sep;18(3):253–9.
15. Mali P, Deshpande S, Singh A. Microleakage of restorative materials: An in vitro study. *J Indian Soc Pedod Prev Dent* 2006;24:15-8.
16. Awliya WY, El-Sahn AM. Leakage pathway of class V cavities restored with different flowable resin composite restorations. *Operative Dentistry.* 2008 Jan 1;33(1):31–6.
17. Eden E, Topaloglu-Ak A, Cuijpers V, Frencken JE. Micro-CT for measuring marginal leakage of Class II resin composite restorations in primary molars prepared in vivo. *Am J Dent* 2008;21:393-7.
18. Abd El Halim S, Zaki D. Comparative evaluation of microleakage among three different glass ionomer types. *Oper Dent* 2011;36:36-42.
19. VS Agrawal, VV Parekh, NC Shah. Comparative evaluation of microleakage of silorane-based composite and nanohybrid composite with or without polyethylene fiber inserts in class II restorations: An In Vitro Study. *Operative Dentistry,* 2012, 37-4, 000-000.
20. Rekha C, Varma B, Jayanthi. Comparative evaluation of tensile bond strength and microleakage of conventional glass ionomer cement, resin modified glass ionomer cement and compomer: An in vitro study. *Contemporary clinical dentistry.* 2012 Jul 1;3:282–7.
21. Gupta SK, Saraswathi V, Ballal V, Acharya S. Comparative evaluation of microleakage in Class V cavities using various glass ionomer cements: An in vitro study. *Journal of Interdisciplinary Dentistry.* 2012 Sep;2:164–9.
22. Poggio C, Chiesa M, Scribante A, Mekler J, Colombo M. Microleakage in Class II composite restorations with margins below the CEJ: In vitro

- evaluation of different restorative techniques. *Med Oral*. 2013;e793–8.
23. Donmez N et al. Microleakage of composite resin restorations in Class V Cavities etched by Er-YAG laser with different pulse modes. *J. LA&HA*, Vol. 2013, No. 1; pp. 6-10.
  24. H Moosavi1, FM Yazdi1, FV Moghadam, S Soltani. Comparison of resin composite restorations microleakage: An in-vitro study. *Open Journal of Stomatology* 3 (2013) 209-214
  25. Diwanji A, Dhar V, Arora R, Madhusudan A, Rathore A. Comparative evaluation of microleakage of three restorative glass ionomer cements: An in vitro study. *J Nat Sc Biol Med*. 2014;5(2):373.
  26. Hussein TA, Bakar WW, Ghani ZA, Mohamad D. The assessment of surface roughness and microleakage of eroded tooth-colored dental restorative materials. *J Conserv Dent* 2014;17:531-5.
  27. Giray FE, Peker S, Durmus B, Kargül B. of new glass ionomer restorative materials in permanent teeth. *EUROPEAN JOURNAL OF PAEDIATRIC DENTISTRY*. 2014;15:122.
  28. Khodadadi E, Esmaeili B, Karimian N, Khafri S. Evaluation of microleakage of Ionoseal filling material as a fissure sealant agent. *CJDR*. 2014;3(2).
  29. Parolia A. A Comparative Evaluation of Microleakage around Class V Cavities Restored with Different Tooth Colored Restorative Materials. 2014;13(1):7.
  30. Shruthi A, Nagaveni N, Poornima P, Selvamani M, Madhushankari G, Subba Reddy V. Comparative evaluation of microleakage of conventional and modifications of glass ionomer cement in primary teeth: An in vitro study. *J Indian Soc Pedod Prev Dent*. 2015;33(4):279.
  31. Rengo C, Goracci C, Ametrano G, Chieffi N, Spagnuolo G, Rengo S, et al. Marginal leakage of class V composite restorations assessed using microcomputed tomography and scanning electron microscope. *Operative Dentistry*. 2015 Jun;40(4):440–8.
  32. Niranjana B, Shashikiran N, Singla S, Thakur R, Dubey A, Maran S. A comparative microleakage evaluation of three different base materials in Class I cavity in deciduous molars in sandwich technique using dye penetration and dentin surface interface by scanning electron microscope. *J Indian Soc Pedod Prev Dent*. 2016;34(4):324.
  33. Sakri M, Koppal P, Patil B, Haralur S. Evaluation of microleakage in hybrid composite restoration with different intermediate layers and curing cycles. *J Dent Allied Sci*. 2016;5(1):14.
  34. Motevaselian F, Tehran, Iran, et al. In Vitro Microleakage of Class V Composite Restorations in Use of Three Adhesive Systems. *J Islam Dent Assoc Iran*. 2016 Jan 1;28(1):14–9.
  35. Ozel E, Tuna EB, Firatli E. The effects of cavity-filling techniques on microleakage in class II resin restorations prepared with Er:YAG laser and diamond bur: A scanning electron microscopy study: Microleakage prepared with Er:YAG laser and diamond bur: SEM study. *Scanning*. 2016 Sep;38(5):389–95.
  36. Govil S, Gupta V, Bhatt A. A comparative evaluation of micro-leakage of different tooth colored restorative materials. An in-vitro study. *IJCPHR* 2016; 1(1):10-14.
  37. Somani R, Jaidka S, Arora S. Comparative evaluation of microleakage of newer generation dentin bonding agents: An in vitro study. *Indian J Dent Res*. 2016;27(1):86.
  38. Kr Rajisha. An in vitro evaluation of microleakage of a bulk fill composite resin in class V cavities cured by two pulse modes. *International Journal of Applied Dental Sciences*. 2016; 2(4): 19-22.
  39. Nematollahi H, Bagherian A, Ghazvini K, Esmaily H, Mehr MA. Microbial microleakage assessment of class V cavities restored with different materials and techniques: A laboratory study. *Dent Res J* 2017;14:344-50.
  40. Khamverdi Z, Fazelian N, Aghaei M. Comparative Evaluation of Micro Leakage in Class V Composite Resin Restorations Using Two Bulk Filled Resin-Composites and One Conventional Composite (Grandio). *Int J Sci Stud* 2017;5(8):331-337.
  41. Tavangar M, Zohri Z, Sheikhezahad H, Shahbeig S. Comparison of Microleakage of Class V Cavities restored with the Embrace WetBond Class V Composite Resin and Conventional Opallis Composite Resin. *The Journal of Contemporary Dental Practice*. 2017 Oct;18(10):867–73.
  42. Kathal S, Bhayya DP, Gupta S, Rao A, Pal A, Saxena ST. Comparative Evaluation of Microleakage of Zirconomer, Amalomer CR, and Conventional Glass Ionomer (Type II) as Restorative Cements in Primary Teeth: An in vitro Study. Kumar A, editor. *IJO CRWEB*. 2017;5(3(Supplement)):376–82.
  43. Samanta S, Das UK, Mitra A. Comparison of Microleakage In Class V Cavity Restored with Flowable Composite Resin, Glass Ionomer Cement and Cention N. 2017;3(8):4.
  44. Dennis D, Aswal D, Anastasia A. The effect of microleakage in class v cavity using self-adhering

- flowable composite with the addition of acid etch. *Jemds*. 2017 Feb 23;6(16):1276–80.
45. Synarellis A, Kouros P, Koulaouzidou E, Strakas D, Koliniotou-Koumpia E. In Vitro Microleakage of class V Composite Restorations prepared by Er,Cr:YSGG Laser and Carbide BUR. *Balkan Journal of Dental Medicine*. 2017 Mar 1;21(1):24–31.
  46. Shathi IJ, Hossain M, Gafur MdA, Rana MdS, Alam MdS. A comparative study of microleakage between giomer and ormocer restoration in class I cavity of first permanent premolar teeth in vivo. *Bangabandhu Sheikh Mujib Medical Univ J*. 2017 Nov 25;10(4):214.
  47. Bansal D, Mahajan M. Comparative evaluation of different periods of enamel microabrasion on the microleakage of class V resin-modified glass ionomer and compomer restorations: An In vitro study. *Indian J Dent Res*. 2017;28(6):675.
  48. Gupta M, Rao D, Hegde S. An in vitro evaluation of microleakage associated with three different compomer placement techniques in primary molars. *Contemp Clin Dent*. 2017;8(1):48.
  49. Lagiseti AK, Hegde P, Hegde MN. Evaluation of bioceramics and zirconia-reinforced glass ionomer cement in repair of furcation perforations: An in vitro study. *J Conserv Dent* 2018;21:184-9.
  50. Sudhapalli SK, Sudhapalli S, Razdan RA, Singh V, Bhasin A. A comparative evaluation of microleakage among newer composite materials: An in vitro study. *Contemp Clin Dent* 2018;9:587-91.
  51. Priyatama V Meshram and Vikas S Meshram, . “Comparative evaluation of microleakage around class v cavities restored with new alkasite material and two different flowable composites-resin- an in vitro study”, *International Journal of Current Research*, 10, (04), 67780-67783 , 2018.
  52. Dr Paul George. “A Comparative Microleakage Analysis of a Newer Restorative Material – An Exvivo Study”.” *IOSR Journal of Dental and Medical Sciences (IOSR-JDMS)*, vol. 17, no. 12, 2018, pg 56-60.
  53. Hussin H, Bakar WW, Ghazali NM, Sajjad A. Microleakage assessment of a new modified glass ionomer cement-nanozirconia-silica-hydroxyapatite restorative material. *J Int Oral Health*. 2018;10(3):138.
  54. Nagy I, El-Sayed H, Shalaby M. Evaluation of marginal seal of different composite restored class V cavity preparations with different cavosurface margins. *Tanta Dent J*. 2018;15(3):140.
  55. Salman Km, Naik S, Kumar Nk, Merwade S, Brigit B, Jalan R. Comparative evaluation of microleakage in Class V cavities restored with giomer, resin-modified glass ionomer, zirconomer and nano-ionomer: An In vitro study. *J Int Clin Dent Res Organ*. 2019;11(1):20.
  56. Mazumdar P, Das A, Das U. Comparative evaluation of microleakage of three different direct restorative materials (Silver Amalgam, Glass Ionomer Cement, Cention N), in Class II restorations using stereomicroscope: An In vitro Study. *Indian J Dent Res*. 2019;30(2):277.
  57. Karnady JA, Prahasti AE. Comparison of microleakage on Class V composite restoration : Study on total etch, self etch and selective etch technique. *Sci Dent J* 2019;3:47-9.
  58. Meshram P, Meshram V, Palve D, Patil S, Gade V, Raut A. Comparative evaluation of microleakage around Class V cavities restored with alkasite restorative material with and without bonding agent and flowable composite resin: An in vitro study. *Indian J Dent Res* 2019;30:403-7.
  59. Namrata Jajoo, Ipsita Maity and Paromita Mazumdar (2019) 'Comparative Evaluation of Microleakage Between Different Restorative Materials Used In Cervical Lesions – A Confocal Laser Scanning Microscopic Study', *International Journal of Current Advanced Research*, 08(09), pp. 20036-20042.
  60. Maha M. Ebaya, Ashraf I. Ali, Salah H. Mahmoud, Evaluation of Marginal Adaptation and Microleakage of Three Glass Ionomer-Based Class V Restorations: In Vitro Study. *Eur J Dent* 2019;13:599–606
  61. Thiedig S, Giraki M, Rüttermann S, Gerhardt-Szep S (2019) Comparative evaluation of microleakage among Resin-Based and nonResin-Based Restorative Materials in dentine cavities. *J Dent Probl Solut* 6(1): 001-005.
  62. Shah KB, Mankar NP, Bajaj PS, et al. Comparative evaluation of microleakage in cavities restored with nanohybrid and microfilled composites using oblique incremental technique- an in vitro- study. *J. Evolution Med. Dent. Sci*. 2020;9(13): 1087-1090
  63. Mrudhula Kamal et al. “A Comparative Study to Evaluate the Microleakage In Class V Cavities Restored With Recent Nano Hybrid Composites.” *IOSR Journal of Dental and Medical Sciences (IOSR-JDMS)*, 19(4), 2020, pp. 55-59.
  64. Hussain MA, Naz S, Rae SN, Khatoun S, Khan SA. Comparative evaluation of microleakage of amalgam, high viscosity and resin-modified glass

- ionomers as restorative materials in primary molars. *Biomedica*. 2020; 36 (2): 146-52.
65. Shraddha Nahar, Mangala T.M., Rushikesh Mahaparale, Adish Saraf, Sagar Pawar, Vincia D'souza, Shubham Mandhane. Comparative evaluation of Microleakage in Class V cavity of various tooth - coloured restorative materials in Human Permanent Premolar Teeth: An In Vitro Study. *Journal of critical reviews*, 2021, 8( 02), 2394-5125
  66. Baig MM, Mustafa M, Jeaidi AZ, Muhaiza M. Microleakage evaluation in restorations using different resin composite insertion techniques and liners in preparations with high C-factor-An in vitro study. *World J Dentistry* 2013;4:57-64.
  67. Craig, Robert G., John M. Powers, and Ronald L. Sakaguchi. *Craig's Restorative Dental Materials*. St. Louis: Mosby Elsevier;1998.
  68. Feilzer AJ, de Gee AJ & Davidson CL. Curing contraction of composites and glass-ionomer cements. *Journal of Prosthetic Dentistry*. 1988;59(3):297-300.
  69. Puckett A, Fitchie J, Hembree J Jr& Smith J. The effect of incremental versus bulk fill techniques on the microleakage of composite resin using a glass-ionomer liner. *Operative Dentistry*. 1992;17(5):186-191.
  70. A. L. C. Jorge and M. A. M. de Ara'ujo, "Influence of cavity preparation and curing method on the marginal seal of resin composite restorations: an in vitro evaluation," *Quintessence International*, vol. 38, pp. e176–e182, 2007.
  71. L. Giachetti, D. S. Russo, C. Bambi, and R. Grandini, "A review of polymerization shrinkage stress: current techniques for posterior direct resin restorations," *Journal of Contemporary Dental Practice*, vol. 7, pp. 79–88, 2006.
  72. MirosBaw OrBowski, Bohena TarczydBo, and Renata ChaBas. Evaluation of Marginal Integrity of Four Bulk-Fill Dental Composite Materials. *The Scientific World Journal* Volume 2015.
  73. C. S. Silveira de Ara'ujo, T. I. Incerti da Silva, F. A. Ogliari, S. S. Meireles, E. Piva, and F. F. Demarco, "Microleakage of seven adhesive systems in enamel and dentin," *Journal of Contemporary Dental Practice*, vol. 7, pp. 26–33, 2006.
  74. Anil Kumar S., Varun Krishnan V.P., Jyothi K.N., Venugopal .P, Sharath Kumar .P, Girish S.A., Melwin Methew. Comparative evaluation of microleakage of G-aenial Universal Flo, Smart Dentin Replacement and Tetric Evo Ceram bulk fill resin composite restorations in class v cavity preparation. *International Dental Journal of Student's Research*;6(1):1-6 2019
  75. Hee YoungPark, ChristopherJ.Kloxin, TimothyF.Scott, Christopher N.Bowman. Covalent adaptable networks as dental restorative resins: Stress relaxation by addition–fragmentation chain transfer in allylsulfide-containing resins. *Dental Materials* 26 ( 2 0 1 0 ) 1010–1016.
  76. Gorsche C, Griesser M, Gescheidt G, Moszner N, Liska R.  $\beta$ -Allyl Sulfones as addition-fragmentation chain transfer reagents: A tool for adjusting thermal and mechanical properties of dimethacrylate networks. *Macromolecules*. Oct2014: pubs.acs.org/macromolecules.
  77. Gorsche C, Koch, T, Moszner N, Liska R. Exploring the benefits of  $\beta$ -allyl sulfones for more homoeogeneous dimethacrylate photopolymer networks. *Poly. Chem*. 2015, 6: 2038-2047.
  78. Dr Dipak Vaghamshi, Dr Vineet Agrawal, Dr Sonali Kapoor. Bulk Fill Composite-A Review. *International Journal of Dental Science and Innovative Research (IJDSIR)* Volume – 2, Issue – 3, May - June- 2019, Page No. : 109 – 115
  79. Fabio Antonio Piola RIZZANTE, Rafael Francisco Lia MONDELLI, Adilson Yoshio FURUSE, Ana Flávia Sanches BORGES, Gustavo MENDONÇA, Sérgio Kiyoshi ISHIKIRIAMA. Shrinkage stress and elastic modulus assessment of bulk-fill composites. *J Appl Oral Sci*. 2019;27.
  80. Sahadev C K , Bharath M J, Sandeep R, Remya Mohan, Santhosh P Sagar. Comparative Evaluation of Marginal Microleakage of Cention-N with Bulk-FIL SDR and ZIRCONOMER. *IJSR* (2016): 79.57
  81. JH Jung ,SH Park. Comparison of Polymerization Shrinkage, Physical Properties, and Marginal Adaptation of Flowable and Restorative Bulk Fill Resin-Based Composites. *Operative Dentistry*, 2017, 42-4, 375-386.
  82. Alagarsamy Venkatesh, Loganathan Saatwika , Arumugam Karthick , Arunajatesan Subbiya. A Review on polymerization shrinkage of resin composites. *European Journal of Molecular & Clinical Medicine* ISSN 2515-8260 Volume 07, Issue 5, 2020.
  83. De Munck J, Van Landuyt K, Peumans M, Poitevin A, Lambrechts P, Braem M et al. A critical review of the durability of adhesion to tooth tissue: methods and results. *J Dent Res* 2005;84(2):118-132.
  84. Manhart J, Chen HY, Mehl A, Weber K, Hickel R Marginal quality and microleakage of adhesive class V restorations. *J Dent* 2001;29(2):123-130.31.